

Resonance impurity scattering in superconductivity in $\text{PrOs}_4\text{Sb}_{12}$

D. Parker¹, S. Haas¹, and K. Maki¹

¹ Department of Physics and Astronomy, University of Southern California, Los Angeles, CA 90089-0484 USA

Key words skutterudite

PACS 74.70.-b

We study the effect of impurity scattering in the unitarity limit on the A and B phase superconductivity in $\text{PrOs}_4\text{Sb}_{12}$. We take the triplet p+h-wave superconducting order parameters and the impurity scattering is treated within the standard theory. We find the quasiparticle density of states and thermodynamics are very sensitive to the impurity scattering. The impurity scattering dependence of the superconducting transition temperature and the superconducting order parameter at $T = 0$ K are very similar to those in d-wave superconductors. Some of these characteristics will provide a sensitive test of the symmetry of the underlying superconducting order parameters.

Copyright line will be provided by the publisher

1 Introduction

Superconductivity in the cubic heavy-fermion (HF) filled skutterudite $\text{PrOs}_4\text{Sb}_{12}$ was discovered in 2002 by Bauer et al [1, 2], and since that time many experimental and theoretical studies of this compound have been performed. Vollmer et al [2] studied the low-temperature specific heat of this compound, finding a double superconducting transition with T_c 's of 1.75 and 1.85 K. This material thus appears to have at least two thermodynamic phases, which we term the A and B phases in the following. Vollmer et al also found the value of the specific heat jump $\Delta C/C$ at T_c to be 3, including both transitions.

Much effort has centered on establishing the phase diagram of $\text{PrOs}_4\text{Sb}_{12}$, with several measurements of the upper critical field H_{c2} [3, 4, 5]. This material is an extreme type 2 superconductor [10], so that in the intermediate state between H_{c1} and H_{c2} partial flux penetration in the form of vortices appears. All H_{c2} measurements indicate an upper critical field near $T=0$ of approximately 2 Tesla. Only two measurements of the A-B phase boundary have been made. Izawa et al [6] performed a measurement of the magnetothermal conductivity of $\text{PrOs}_4\text{Sb}_{12}$ and found that the higher-temperature, higher-field A phase contains at least four order parameter nodes along the cubic axes, and that the lower-temperature, lower-field B phase contains only two nodes along the [010] axis. Measson et al [7] detected the A-B phase boundary through thermodynamic measurements of the specific heat (which undergoes a jump in the transition from one phase to another) and initially produced an alternative phase diagram, in which the A-B phase boundary lies much closer to the upper critical field H_{c2} , and essentially parallels this curve. Recent work by Measson, however [8] details several samples which appear to contain only an A phase, so that the phase diagram of this material remains highly controversial. Below we present two alternative diagrams based upon the work of Measson et al and Izawa et al.

Much effort has also centered on the determination of the order parameter symmetry of these phases. Kotegawa [9] investigated the nuclear spin-lattice relaxation time via nuclear quadrupolar resonance experiments, and found evidence for exponentially activated behavior above $0.3T_c$, indicating isotropic or s-wave pairing. Kotegawa also found a large value of Δ/T_c of approximately 2.5, significantly exceeding the BCS s-wave weak-coupling value of 1.76. Similarly, MacLaughlin et al [10] studied the pairing state

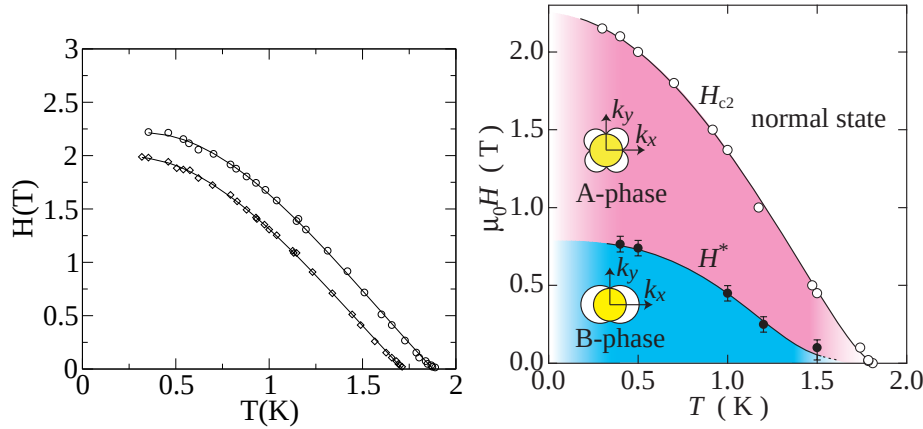


Fig. 1 Phase diagrams by Measson et al (left) and Izawa et al. The top line and data points represent H_{c2} of the A phase, while the lower one represents the AB phase boundary H^* .

via muon-spin resonance and also found evidence for an isotropic gap. Suderow et al [11] performed scanning tunneling microscopy (STM) measurements and asserted that the Fermi surface is gapped over most, if not all, quasiparticle momenta. As a directionally locked probe, however, this measurement may have difficulty determining certain nodal structures, such as point nodes.

Other experiments show strong evidence for nodal superconductivity in $\text{PrOs}_4\text{Sb}_{12}$. In particular, Chia et al [12] measured the superfluid density of single crystals and found low-temperature power-law behavior, with $\rho_s \sim 1 - \alpha T^2$. This power-law behavior was observed for fields parallel to each of the three crystal axes. In addition, the previously mentioned magnetothermal conductivity data of Izawa et al [6] strongly suggests the presence of point nodes.

Several theoretical proposals have been put forth in an attempt to understand the superconductivity in $\text{PrOs}_4\text{Sb}_{12}$. Miyake et al [13] proposed triplet p-wave pairing caused by quadrupolar fluctuations, whereas Goryo [14] proposed an “anisotropic s-wave” state for the A phase and an “anisotropic s+id-wave” state for the B phase, assuming singlet pairing. Sergienko and Curnoe [15] proposed states with a mixture of line nodes and point nodes. For the purposes of this paper, we will assume the existence of unconventional superconductivity in $\text{PrOs}_4\text{Sb}_{12}$ with A-phase and B-phase order parameters as given in Ref. [16], i.e. triplet p+h-wave order parameters. The clean-limit thermodynamics of these order parameters was worked out (as in [19]) in [17], while the upper critical field H_{c2} was worked out in [18]. In both works reasonable agreement between theory and experiment was found, suggesting further analysis.

Some work concerning superconductivity in substituted samples of $\text{PrOs}_4\text{Sb}_{12}$ has been performed. Frederick et al [20] and Chia et al [21] both studied the superconducting order in single crystals of $\text{Pr}(\text{Os}_{1-x}\text{Ru}_x)_4\text{Sb}_{12}$. Frederick found evidence for unconventional superconductivity in pure $\text{PrOs}_4\text{Sb}_{12}$, but observed exponentially activated behavior in all of the other samples with $x \geq 0.05$. Chia found evidence for a three phase scenario at low dopings ($x < 0.2$), and confirmed the exponentially activated behavior found by Frederick. Rotundu et al [22] examined the low-temperature susceptibility and specific heat of single crystals of $\text{Pr}_{1-x}\text{La}_x\text{Os}_4\text{Sb}_{12}$ and found that the Lanthanum substitution had little effect on the superconductivity, with an essentially linear decrease in T_c as x as increased.

The recent interest in substituted samples suggests that theoretical modeling of the effects of impurity scattering is in order. We expect the theory outlined below, which assumes strong impurity scattering, should be applicable when samples doped towards non-superconducting materials (unlike $\text{PrRu}_4\text{Sb}_{12}$ and $\text{LaOs}_4\text{Sb}_{12}$) are tested.

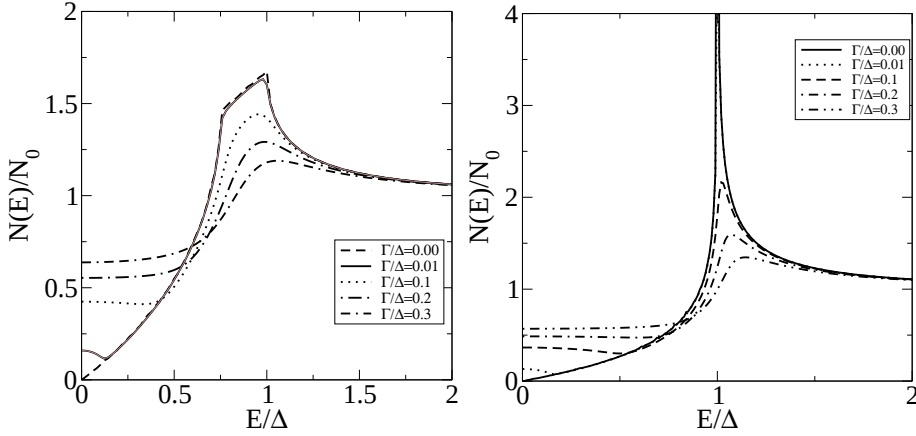


Fig. 2 The quasiparticle density-of-states for the A phase (left) and the B phase are shown, for several impurity scattering rates.

2 Impurity Scattering in $\text{PrOs}_4\text{Sb}_{12}$

In this section we present the results of calculations of the effects of impurity scattering on the superconductivity in $\text{PrOs}_4\text{Sb}_{12}$. As mentioned previously, we use here the order parameter model described in Ref. [16] As we expect the effects of impurity scattering to be quite strong we model the scattering in the unitarity limit, in which the phase shift between the incoming and scattered waves is taken to be $\pi/2$. Then following the approach described in Ref. [23] we incorporate the scattering by renormalizing the quasiparticle frequency $\tilde{\omega}$ as follows:

$$\tilde{\omega} = \omega + i\Gamma \left\langle \frac{\tilde{\omega}}{\sqrt{\tilde{\omega}^2 - \Delta^2 f^2}} \right\rangle^{-1} \quad (1)$$

Here Γ is the quasiparticle scattering rate in the normal state and $\Delta = \Delta(T)$. For the A-phase $f = \frac{3}{2}(1 - \hat{k}_x^4 - \hat{k}_y^4 - \hat{k}_z^4)$, and $\langle \dots \rangle$ denotes $\int d\Omega/4\pi$. For the B-phase, $f = 1 - z^4$, and $\langle \dots \rangle$ denotes $\int_0^1 dz \dots$

The quasiparticle density-of-states (DOS) can be obtained once $\tilde{\omega}$ is known, from the relation

$$N(E) = N_0 \text{Re} \left\langle \frac{\tilde{\omega}}{\sqrt{\tilde{\omega}^2 - \Delta^2 f^2}} \right\rangle \quad (2)$$

Below is the density-of-states for the A and B phases for a few impurity scattering rates, as indicated. As is evident from the plots, even a small amount of impurity scattering creates significant low-energy excitations and truncates the peak normally observed at $E = \Delta$. It is interesting that $N(E)$ is largely independent of E for relatively low energy. These DOS should be experimentally accessible via scanning tunneling microscopy (STM) measurements.

Also of interest is the overall dependence of the zero-energy DOS on impurity scattering rates, along with the zero-temperature behavior $\Delta(\Gamma, T = 0)$ and $T_c(\Gamma)$. These quantities are shown below for both phases. As stated previously, the zero-energy DOS increases quite rapidly for small impurity concentrations. Here $T_c(\Gamma)$ is found by solving the well-known Abrikosov-Gorkov equation [24]:

$$-\ln(T_c/T_{c0}) = \Psi\left(\frac{1}{2} + \frac{\Gamma}{2\pi T_c}\right) - \Psi\left(\frac{1}{2}\right) \quad (3)$$

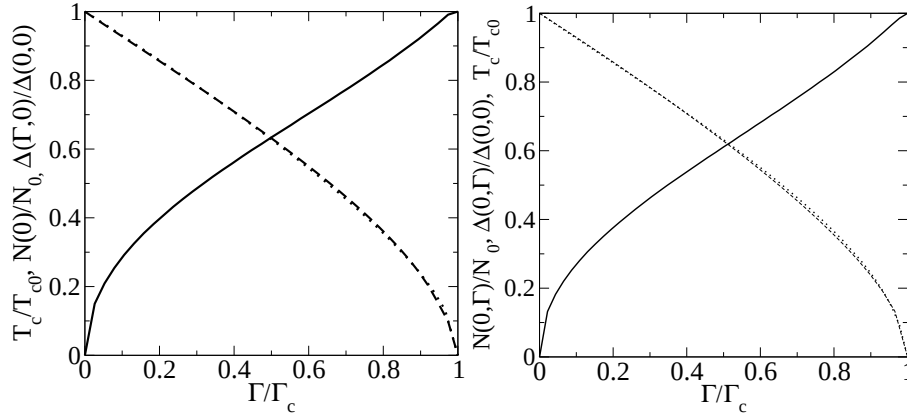


Fig. 3 The zero-energy DOS, zero-temperature $\Delta(\Gamma)$ and $T_c(\Gamma)$ for the A phase (left) and the B phase are shown. The zero-energy DOS begins at the lower left corner of each plot.

Here $\Psi(z)$ is the digamma function. And Γ_c , the critical impurity scattering rate where superconductivity disappears, is given by $0.8819 T_{c0}$ for both phases.

The temperature-dependent order parameter $\Delta(T)$ is determined by solving the BCS weak-coupling gap equation:

$$\lambda^{-1} = 2\pi T \langle f^2 \rangle^{-1} \sum_n \left\langle \frac{f^2}{\sqrt{\tilde{\omega}_n^2 + \Delta^2 f^2}} \right\rangle \quad (4)$$

Here ω_n and $\tilde{\omega}_n$ are related by

$$\tilde{\omega}_n = \omega_n + \Gamma \left\langle \frac{\tilde{\omega}_n}{\sqrt{\tilde{\omega}_n^2 + \Delta^2 f^2}} \right\rangle^{-1} \quad (5)$$

Here ω_n is the Matsubara frequency $\omega_n = (n + \frac{1}{2})2\pi T$. In addition, the sum over n must be truncated at $\omega = E_0$, the cut-off energy. Plots of the temperature dependent order parameters $\Delta_A(T)$ and $\Delta_B(T)$ are presented below.

Once $\Delta(\Gamma, T)$ has been determined, the thermodynamics of the system can be analyzed. We begin with the entropy:

$$S_s = -4 \int_0^\infty dE N(E) (f \ln f + (1-f) \ln(1-f)) \quad (6)$$

Here f is the Fermi-Dirac distribution $(1 + e^{\beta E})^{-1}$ with $\beta = 1/k_B T$ and $N(E)$ is the quasiparticle density of states. From the entropy the electronic specific heat is determined via

$$C_s = T \frac{\partial S}{\partial T} \quad (7)$$

We show above the specific heat for both phases for all temperatures below T_c for a few impurity scattering rates. As expected, the specific heat is T -linear for small T , with the coefficient equal to the zero-energy DOS. The specific heat jump ΔC at T_c decreases rapidly with impurity concentration for both phases.

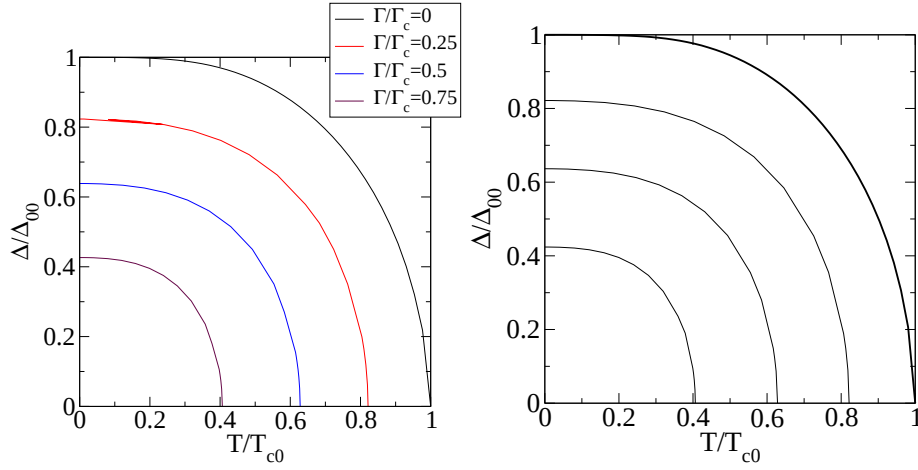


Fig. 4 The temperature dependent order parameters $\Delta_A(T)$ (left) and $\Delta_B(T)$, for $\Gamma/\Gamma_c = 0, 0.25, 0.5$ and 0.75 .

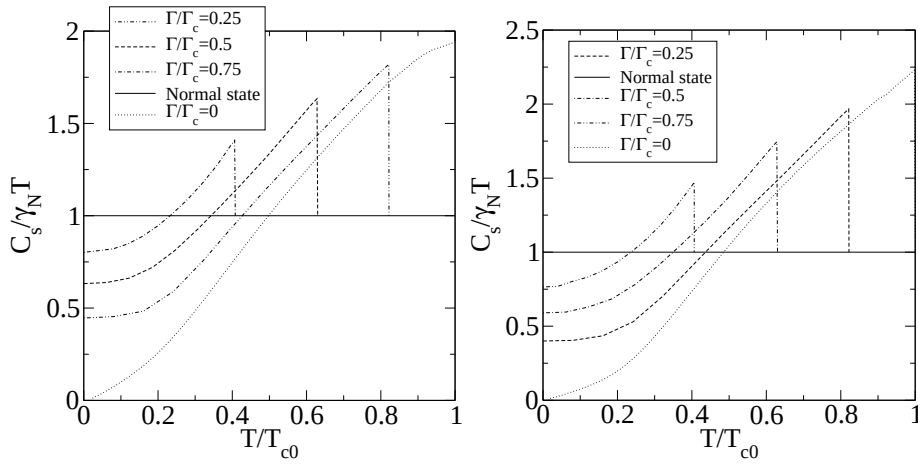


Fig. 5 The specific heat for the A phase (left) and B phase is shown, for impurity scattering rates $\Gamma/\Gamma_c = 0, 0.25, 0.5$ and 0.75 .

The superfluid density is calculated as follows:

$$\rho_{sab}(\Gamma, T) = 2\pi T \sum_0^\infty \left\langle \frac{3}{2} \sin^2 \theta \frac{\Delta^2 |f|^2}{(\tilde{\omega}_n^2 + \Delta^2 |f|^2)^{3/2}} \right\rangle \quad (8)$$

$$\rho_{sc}(\Gamma, T) = 2\pi T \sum_0^\infty \left\langle 3 \cos^2 \theta \frac{\Delta^2 |f|^2}{(\tilde{\omega}_n^2 + \Delta^2 |f|^2)^{3/2}} \right\rangle \quad (9)$$

Note that the superfluid density is isotropic for the cubic-symmetry retaining A-phase, but is not for the symmetry-breaking B-phase. We show below the superfluid density for both phases for a range of impurity concentrations. We observe that while the pure limit superfluid density varies linearly with temperature at low temperature for both the A phase and the c-axis B phase results, this dependence changes to a T^2 dependence when the effect of impurities is considered.

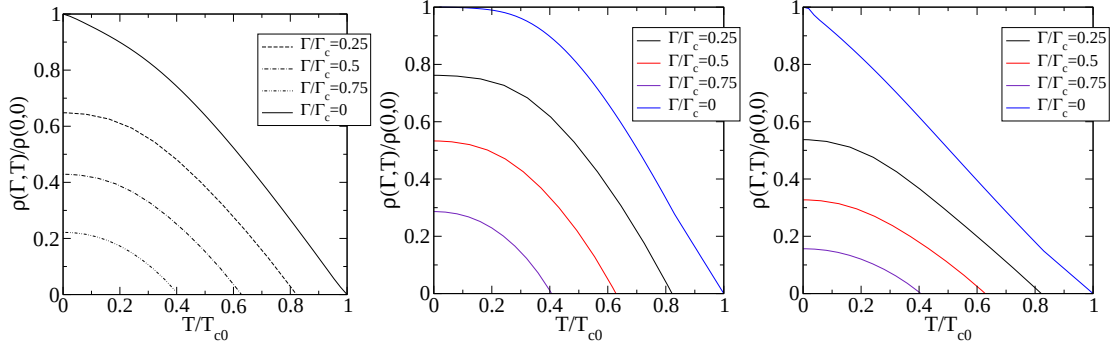


Fig. 6 From top left, the superfluid density for the A phase, for the B phase ab plane, and for the B phase c axis. Impurity scattering rates are $\Gamma/\Gamma_c = 0, 0.25, 0.5$ and 0.75 , with lower impurity scattering rates at the top of each plot. Note that the top left and bottom plots resemble that of d-wave superconductivity.

Finally, we consider the nuclear spin lattice relaxation rate T_1^{-1} , which is related to the density-of-states $N(E)$ by the following relation:

$$(T_1 T)^{-1}/(T_1 T)|_{T=T_c}^{-1} T = T_c = \int_0^\infty dE N^2(E) \text{sech}^2(E/(2T))/2T \quad (10)$$

Plots of this quantity for both phases, for both the pure and impurity scattering cases are shown. In the zero energy limit $(T_1 T)^{-1}/(T_1 T)|_{T=T_c}^{-1}$ becomes $N(0)^2$. We also note the presence of a small peak in

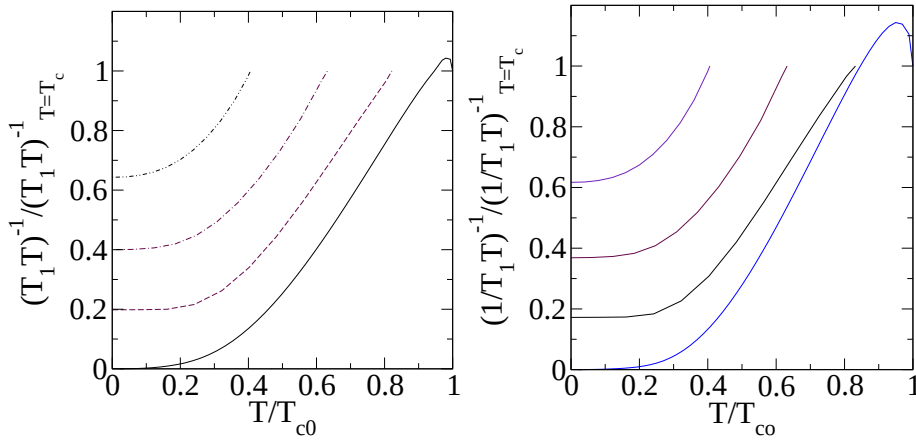


Fig. 7 Plots of the nuclear spin lattice relaxation rate T_1^{-1} for the A phase (left) and B phase are shown. Impurity scattering rates are $\Gamma/\Gamma_c = 0, 0.25, 0.5$ and 0.75 , with lower impurity scattering rates at the top of each plot.

both pure case results just below T_c . As will be shown elsewhere [25], this is a general feature of pure-case unconventional superconductors obeying BCS weak-coupling theory. It results from the distribution of $N(E)$ away from the constant DOS observed in the normal state. Note that even the A-phase, for which the density-of-states does not show the usual divergence at $E = \Delta$, shows a small peak. The B phase peak is much larger due to the increased density-of-states near $E = \Delta$; this divergence, in fact, is $\propto (E - \Delta)^{-1/4}$ and is hence a somewhat stronger divergence than the logarithmic divergence found in d-wave superconductivity.

3 Conclusion

We have calculated the effect of impurity scattering on the superconductivity in $\text{PrOs}_4\text{Sb}_{12}$ within the unitary limit. We find that the superconductivity is expected to be quite sensitive to impurity concentration within this limit.

Acknowledgements

We thank H. Won, K. Izawa, Y. Matsuda and H. Tou for many useful discussions. DP and SH were supported by the Petroleum Research Fund.

References

- [1] E.D. Bauer, N.A. Frederick, P.-C. Ho, V.S. Zapf, and M.B. Maple, Phys. Rev. B **65**, R100506 (2002).
- [2] R. Vollmer, A. Fajó, C. Pfleiderer, H. v. Löhneysen, E. D. Bauer, P.-C. Ho, V. Zapf, and M. B. Maple, Phys. Rev. Lett. **90**, 57001 (2003).
- [3] K. Tenya, N. Oeschler, P. Gegenwart, F. Steglich, N.A. Frederick, E.D. Bauer, and M.B. Maple, Acta Physica Polonica B **34** 2, p.995 (2002).
- [4] P.-C. Ho, V.S. Zapf, E.D. Bauer, N. A. Frederick, M. B. Maple, G. Giester, P. Rogl, S.T. Berger, C.H. Paul and E. Bauer, Int. J. Mod. Phys. B **16**, 3008 (2002).
- [5] T. Tayama, T. Sakakibara, H. Sugawara, Y. Aoki, and H. Sato, J. Phys. Soc. Jpn. **72**, 1516 (2003).
- [6] K. Izawa, Y. Nakajima, J. Goryo, Y. Matsuda, S. Osaki, H. Sugawara, H. Sato, P. Thalmeier, and K. Maki, Phys. Rev. Lett. **90**, 117001 (2003).
- [7] M.-A. Measson, D. Brathwaite, J. Flouquet, G. Seyfarth, J.P. Brison, E. Lhotel, C. Paulsen, H. Sugawara, and H. Sato, Phys. Rev. B **70**, 064516 (2004).
- [8] M.-A. Measson et al, presented at the SCES '05 conference.
- [9] H. Kotegawa, M. Yogi, Y. Imamura, Y. Kawasaki, G.-Q. Zheng, K. Kitaoka, S. Ohsaki, H. Sugawara, Y. Aoki, and H. Sato, Phys. Rev. Lett. **90**, 027001 (2003).
- [10] D.E. MacLaughlin, J.E. Sonier, R.H. Heffner, O.O Bernal, Ben-Li Young, M.S. Rose, G.D. Morris, E.D. Bauer, T.D. Do and M.B. Maple, Phys. Rev. Lett. **89**, 157001 (2002).
- [11] H. Suderow, S. Vieira, J.D. Strand, S. Bud'ko and P.C. Canfield, Phys. Rev B **69**, 060504(R) (2004).
- [12] Elbert E.M. Chia, M.B. Salomon, H. Sugawara, and H. Sato, Phys. Rev. Lett. **91**, 247003 (2003).
- [13] K. Miyake, H. Kohno and H. Harima, J. Phys.: Cond. Matt. **15**, L275 (2003).
- [14] Jun Goryo, Phys. Rev. B **67**, 184511 (2003).
- [15] I.A. Sergienko and S.H. Curnoe, Phys. Rev. B **70**, 144522 (2004).
- [16] K. Maki, S. Haas, D. Parker, H. Won, K. Izawa and Y. Matsuda, Europhys. Lett. **68**, 720 (2004).
- [17] D. Parker, K. Maki and S. Haas, accepted for publication by Eur. Phys. J. B.
- [18] D. Parker, K. Maki and H. Won, cond-mat/0510527.
- [19] H. Won, S. Haas, D. Parker, S. Telang, A. Vanyolos and K. Maki in "Lectures on the physics of highly correlated electron systems IX", AIP conference proceedings 789 (Melville 2005), pp. 3-43.
- [20] N.A. Frederick, T.A. Sayles, and M.B. Maple, Phys. Rev. B **71**, 064508 (2005).
- [21] E.E.M. Chia, M.B. Salamon, D. Vandervelde, D. Kikuchi, H. Sugawara, and H. Sato, cond-mat/0411395.
- [22] C.R. Rotundu, P. Kumar, and B. Andraka, cond-mat/0402599.
- [23] G. Yang and K. Maki, Eur. Phys. J. B **21**, 61 (2001).
- [24] A.A. Abrikosov and L.P. Gor'kov, Sov. Phys. JETP **12**, 1243 (1961).
- [25] D. Parker, in preparation.